

# Electrochemical Properties of $\text{Li}_4\text{Ti}_5\text{O}_{12}$ and $\text{LiTi}_2\text{O}_4$ Epitaxial Thin Films

Susumu Shiraki<sup>1,2</sup>, Yoshitaka Takagi<sup>2</sup>, Ryota Shimizu<sup>2,3</sup> and Taro Hitosugi<sup>2,3</sup>

<sup>1</sup> Nippon Institute of Technology, Saitama 345-8501, Japan

E-mail: shiraki.susumu@nit.ac.jp

<sup>2</sup> Advanced Institute for Materials Research, Tohoku Univ., Miyagi 980-8577, Japan

<sup>3</sup> Tokyo Institute of Technology, Tokyo 152-8552, Japan

## Abstract

We fabricated  $\text{Li}_4\text{Ti}_5\text{O}_{12}$ (111) and  $\text{LiTi}_2\text{O}_4$ (111) epitaxial thin films by using pulsed laser deposition. By annealing the  $\text{LiTi}_2\text{O}_4$  epitaxial films at 750°C under oxygen partial pressure of  $1 \times 10^{-3}$  Torr, the films transformed to high crystallinity  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  epitaxial thin films with a rocking curve full width at half-maximum of 0.057°. However, the high crystallinity  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  films showed poor electrochemical performance compared to that of the as-grown ones. These results indicate that oxygen partial pressure during annealing treatments strongly influences crystal structures and electrochemical properties of lithium titanate battery materials.

## 1. Introduction

$\text{Li}_4\text{Ti}_5\text{O}_{12}$  has shown great promise as lithium ion battery anode materials because they have stable battery operation. The most characteristic feature of  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  is negligible volume expansion and contraction during insertion and extraction of Li ion. The synthesis of the films is important because they are useful for battery applications in the field of micromachine, basic research for understanding of battery mechanism.

Pulsed laser deposition (PLD) is a powerful deposition technique for the synthesis of high-quality oxide thin films [1]. Recently, epitaxial thin films of electrode materials such as  $\text{LiCoO}_2$  [2-5],  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  [6], and  $\text{LiMn}_2\text{O}_4$  [7], have been reported. In our previous work, we showed synthesis of  $\text{LiTi}_2\text{O}_4$  and  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  epitaxial thin films from a single  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  target by varying the oxygen partial pressure  $P_{\text{O}_2}$ . However, the as-grown  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  has a wider rocking curve full width at half-maximum (FWHM) compared to that of  $\text{LiTi}_2\text{O}_4$ .

In this study, we report the fabrication of lithium titanate (LTO) epitaxial thin films using PLD. We successfully improved crystallinity of  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  through the post-deposition annealing of  $\text{LiTi}_2\text{O}_4$ . We further examined electrochemical properties of  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  and  $\text{LiTi}_2\text{O}_4$  films by charge and discharge battery operation.

## 2. Experimental

Lithium titanate (LTO) thin films were deposited by using PLD on  $\text{MgAl}_2\text{O}_4$  (111) and Nb-doped  $\text{SrTiO}_3$ (001) substrates. A polycrystalline  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  target (Toshiba Manufacturing) was used for the deposition. A KrF excimer laser (wavelength: 248 nm) was used for the deposition with a repetition rate of 5Hz and a fluence of 0.6 J/cm<sup>2</sup>. The  $P_{\text{O}_2}$  was

varied from  $1 \times 10^{-6}$  to  $1 \times 10^{-3}$  Torr, and the substrate temperature during deposition was kept at 800°C. The LTO films were typically 200 nm thick. The crystal structures of the films were characterized with an x-ray diffractometer (NEW D8 Discover, Bruker). The electrochemical properties of epitaxial LTO films were examined with 2032 coin type Li cells using Li metal foils as anode. The electrolyte used was EC (ethylene carbonate)-DEC (diethyl carbonate) with a molar ratio of 3:7 as a solvent and supporting electrolyte of 1M  $\text{LiPF}_6$ . The cut-off voltages in charge and discharge measurements were 0.8 and 2.5 V, and the current was set at 1.2 □A (approximately 0.33C).

## 3. Results and discussions

Figure 1 shows the out-of-plane XRD patterns of  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  thin films deposited in different conditions. For comparison, the result of  $\text{LiTi}_2\text{O}_4$  is also shown. The as-grown  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  was obtained at high  $P_{\text{O}_2}$  of  $1 \times 10^{-3}$  Torr, while  $\text{LiTi}_2\text{O}_4$  was at low  $P_{\text{O}_2}$  of  $1 \times 10^{-6}$  Torr [6]. In the as-grown  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  and  $\text{LiTi}_2\text{O}_4$ , we found (111), (222), (333) and (444) peaks from  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  and  $\text{LiTi}_2\text{O}_4$ , respectively, in addition to peaks from the  $\text{MgAl}_2\text{O}_4$  substrate, indicating the epitaxial growth of LTO although in-plane XRD results were not shown here. In addition, a small peak from rutile  $\text{TiO}_2$  was observed as a shoulder in the right side of (222) peak from  $\text{MgAl}_2\text{O}_4$  substrate in the as-grown  $\text{Li}_4\text{Ti}_5\text{O}_{12}$ . A closer look of Fig. 1 indicates a shift of (444) peaks of  $\text{LiTi}_2\text{O}_4$  to a lower 2θ angle compared to that of as-grown  $\text{Li}_4\text{Ti}_5\text{O}_{12}$ , as shown in Fig. 1. Furthermore, we could clearly see a remarkable difference in crystallinity by comparing FWHM values between the two films. The FWHM values of the XRD rocking curve of the LTO(111) peaks were 0.17° and 0.044° for the as-grown  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  and  $\text{LiTi}_2\text{O}_4$ , respectively.

Considering that the as-grown  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  was obtained at high  $P_{\text{O}_2}$  during the deposition, we speculated that high-crystallinity  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  could be obtained by post-deposition annealing of high-quality  $\text{LiTi}_2\text{O}_4$ . Hence, we annealed a  $\text{LiTi}_2\text{O}_4$  film at 750°C to obtain high quality  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  and found that  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  was formed at higher  $P_{\text{O}_2}$  than  $1 \times 10^{-3}$  Torr, as shown in Fig. 1. Furthermore, the post-deposition-annealed  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  obtained at  $P_{\text{O}_2}$  of  $1 \times 10^{-3}$  Torr showed high crystallinity single phase with FWHM of 0.056°.

The growth of  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  was also confirmed by electrochemical properties. In charge and discharge curves of Figure 2, we can clearly see the plateaus at 1.59 V, and good reproducibility. These plateaus are characteristic to  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  and indicate the formation of  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  [8,9]. Here we compare

the electrochemical properties of the as-grown and post-deposition-annealed  $\text{Li}_4\text{Ti}_5\text{O}_{12}$ . The charge curves for the as-grown  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  shows are very flat plateau at 1.59 V in the capacity range between 20 and 160 mAh/g, and the charge capacity was about 250 mAh/g and does not change with cycle. In contrast, the capacity range for the post-annealed  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  was between 20 and 100 mAh/g in the first charge, and decreased with cycle. These results indicate that the post-deposition-annealed  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  shows poor electrochemical properties in spite of its good crystallinity.

### 3. Conclusions

We fabricated  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  epitaxial thin films by using PLD. The charge and discharge curves of the as-grown  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  show plateaus at 1.59 V, and the capacity was 250 mAh/g, which were consistent with the previous powder data. Furthermore, we obtained high-quality  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  by annealing the as-grown one at oxygen partial pressure of  $1 \times 10^{-3}$  Torr, but the charge and discharge curves show poor electrochemical properties in spite of its good crystallinity. These results indicate that oxygen partial pressure during annealing treatments strongly influences crystal structures and electrochemical properties of lithium titanate battery materials.

### Acknowledgements

This study was supported by the “Applied and Practical LiB Development for Automobile and Multiple Application” project of the New Energy and Industrial Technology Development Organization (NEDO). The authors also acknowledge the support of Toyota Motor Corporation.

### References

- [1] R. Eason, Pulsed Laser Deposition of Thin Films (Wiley-Interscience, 2006).
- [2] T. Tsuruhama, T. Hitosugi, H. Oki, Y. Hirose, T. Hasegawa, Appl. Phys. Express 5 (2009) 085502, 1-3.
- [3] S. Shiraki, H. Oki, Y. Takagi, T. Suzuki, A. Kumatani, R. Shimizu, M. Haruta, T. Ohsawa, Y. Sato, Y. Ikuhara, T. Hitosugi, J. Power Sources 267 (2014) 881-887.
- [4] S. Shiraki, Y. Takagi, R. Shimizu, T. Suzuki, M. Haruta, Y. Saito, Y. Ikuhara, T. Hitosugi, Thin Solid Films 600 (2016) 175-178.
- [5] S. Shiraki, H. Oki, T. Hitosugi, Surf. Int. Anal. 48 (2016) 1240-1243.
- [6] A. Kumatani, T. Ohsawa, R. Shimizu, Y. Takagi, S. Shiraki, T. Hitosugi, Appl. Phys. Lett. 101 (2012) 123103, 1-4.
- [7] D. Packwood, S. Shiraki, T. Hitosugi, Phys. Rev. Lett. 111 (2013) 036101.
- [8] K. Colbow, J. Dahn, R. Haering, J. Power Sources 26 (1989) 397.
- [9] T. Ohzuku, A. Ueda, N. Yamamoto, J. Electrochem. Soc. 142 (1995) 1431.

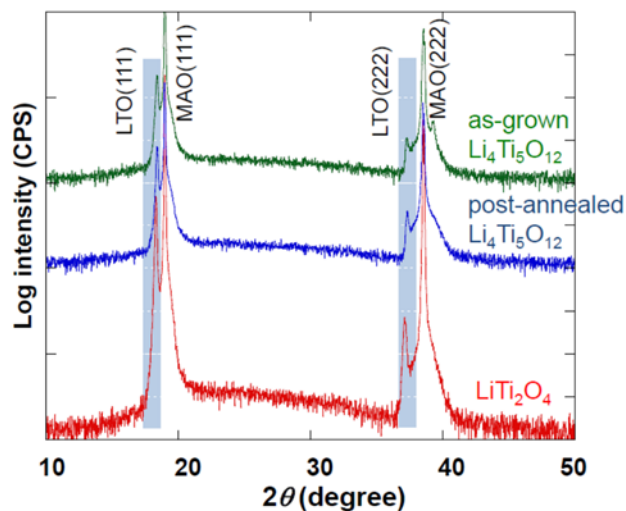


Fig. 1. XRD patterns from  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  and  $\text{LiTi}_2\text{O}_4$  epitaxial films.

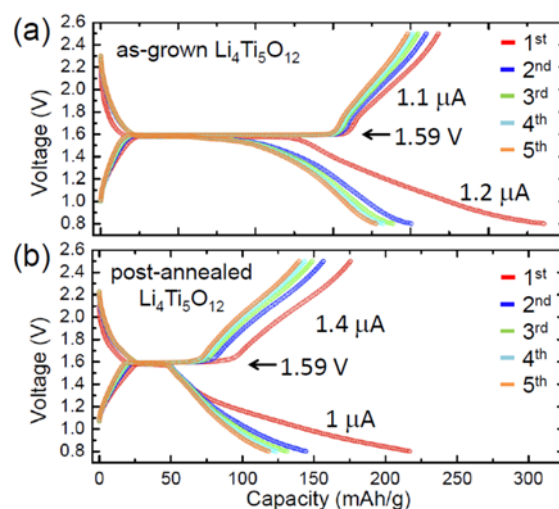


Fig. 2. The charge and discharge curves of (a) as-grown and (b) post-deposition annealed  $\text{Li}_4\text{Ti}_5\text{O}_{12}$  epitaxial films.