

Fabrication of MoS₂ layers on free-standing GaN for heterojunction photorespon- sive device applications

Pradeep Desai^{1,*}, Ajinkya K. Ranade¹, Rakesh D. Mahyavanshi¹, Masaki Tanemura¹, Golap Kalita^{1,2,*}

¹Department of Physical Science and Engineering,
Nagoya Institute of Technology,
Gokiso-cho, Showa-ku,
Nagoya 466-8555, Japan

²Frontier Research Institute for Material Science,
Nagoya Institute of Technology,
Gokiso-cho, Showa-ku,
Nagoya 466-8555, Japan

*Corresponding authors address: phone/Fax +81-527355216
E-mail: desai.pradeep@zoho.com, kalita.golap@nitech.ac.jp

Abstract

Molybdenum sulfide (MoS₂) layers and gallium nitride (GaN) are well suited for heterojunction device fabrication due to their less lattice mismatch. In this study, we report on the synthesis of MoS₂ layers on free-standing GaN for fabrication of a heterojunction photoresponsive device. Rectifying diode characteristic and photovoltaic action with vertical current flow were obtained in the heterostructure. In the MoS₂-GaN heterojunction a suitable interface potential was observed by the photoelectron spectroscopy analysis. Our study revealed that the MoS₂-GaN heterojunction can be suitable for various optoelectronic devices with stable performance.

1. Introduction

Lattice mismatch of GaN and MoS₂ is only 0.8%, hence both these material can be used as substrate for growth on one another and could be used for development of novel heterostructure.¹⁻⁴ In the absence of dangling bond at the interface in layered heterostructures it provides ultra-fast charge transfer and thereby leading to fabrication of efficient devices.^{5,6} The heterostructure of MoS₂ and GaN provides an opportunity to develop photoresponsive device beyond the ultraviolet (UV) wavelength.⁷ The MoS₂-GaN heterojunction is practically applicable technology for optoelectronics devices such as photovoltaic devices, photodiode, and photocatalyst applications with broadband photoresponsivity.⁸⁻¹⁰

Previously, MoS₂ layers has been synthesized on various substrates by the chemical vapour deposition (CVD) technique.^{11, 12} In this work, we studied the deposition of MoS₂ continuous film on GaN by sulfurization process of metal oxide precursor. The obtained MoS₂ layers on GaN surface was characterized and the current-voltage properties were analyzed.

2. Results and Discussions

Fig. 1a shows the ball and stick diagram of MoS₂ layers atop of GaN. Each molybdenum (Mo) atom is surrounded by six sulfur (S) atom forming a trigonal prismatic coordination

sphere. The bulk MoS₂ consist of several layers like graphite, where the S-Mo-S configuration forms a monolayer. The GaN bulk single crystal has a wurtzite structure with one Ga atom has three nearest neighbors connected by a covalent bond.

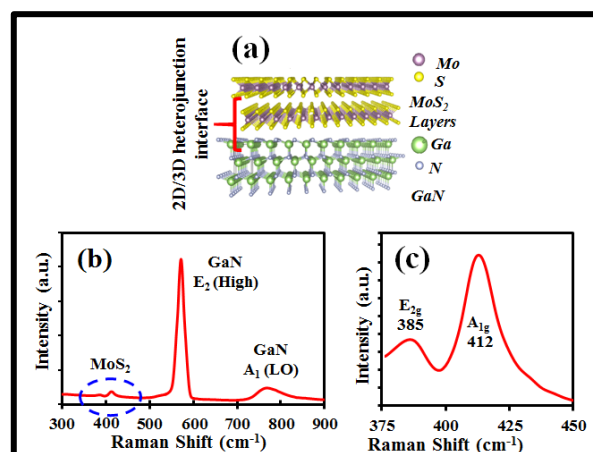


Fig 1. (a) Ball and stick diagram of MoS₂ and GaN (b) Raman spectra of MoS₂/GaN heterojunction (c) Raman spectra corresponding to MoS₂ peaks

The in-place lattice mismatch of MoS₂ and GaN is only 0.8%, signifying the possibility of epitaxial heterostructure growth. We carried out Raman spectroscopic analysis of the synthesized MoS₂ layers on GaN. Fig. 1b shows a Raman spectrum for the MoS₂-GaN heterostructure. The peaks corresponding to E₂(High) and A₁(LO) of GaN layer were observed at 570.2 and 749.2 cm⁻¹, respectively. Additional small intensity peaks were observed at lower wavenumber as shown in the fig. corresponding to the MoS₂ layer. Fig. 1c shows the E_{2g} and A_{1g} peaks of MoS₂ layer at 385 and 412 cm⁻¹, respectively.⁴³ The spectroscopy analysis confirmed the formation of MoS₂ layers on GaN and their heterostructure.

The heterostructure of MoS₂ and GaN was investigated by fabricating a two-terminal diode structure under dark and

monochromatic light illumination. Fig. 2a, 2b shows the J-V characteristics without and with light, respectively, and fig. 2c shows J-V characteristics under dark and illumination for a smaller voltage and current range, presenting the photovoltaic action on MoS₂ layers and GaN heterojunction device. The short circuit current (J_{sc}) and open circuit voltage (V_{oc}) were obtained as 0.35 mV and 0.22 $\mu\text{A}/\text{cm}^2$, respectively for the device under monochromatic light. Further, studies on the interface and heterojunction properties were under process to achieve higher device performance.

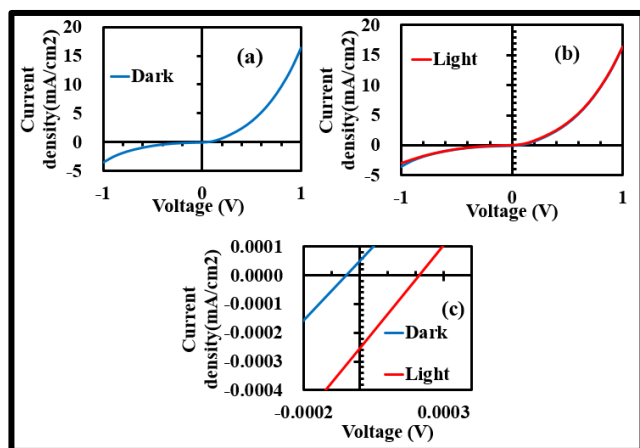


Fig 2. (a) J-V characteristics without light illumination presenting the rectification behavior (b) J-V characteristics with and without light illumination (c) J-V characteristics with and without light illumination for a smaller voltage range presenting the photovoltaic action.

3. Conclusion

In conclusion, we have demonstrated the fabrication of MoS₂ layers on free-standing GaN by the sulfurization technique for fabrication of a heterojunction photoresponsive device. Raman analysis showed the E_{2g} and A_{1g} peaks at 385 and 412 cm^{-1} , respectively confirming formation of MoS₂ layers. J-V analysis showed the rectifying diode characteristics and a photovoltaic action with monochromatic light illumination.

Acknowledgements

The work is supported by Grant-in-Aid (C) from the Japan Society for the promotion of Science (Grant No. 19K05267). The authors would like to thank NGK Insulators, Ltd., Nagoya, Japan, for the GaN samples.

References

- [1] P. Gupta, A. A. Rahman, S. Subramanian, S. Gupta, A. Thamizhavel, T. Orlova, S. Rouvimov, S. Vishwanath, V. Protasenko, M. R. Laskar, H. G. Xing, D. Jena and A. Bhattacharya, *Scientific Reports*, 2015, **6**(1), 23708.
- [2] T. P. O'Regan, D. Ruzmetov, M. R. Neupane, R. A. Burke, A. A. Herzing, K. Zhang, A. G. Birdwell, D. E. Taylor, E. F. C. Byrd, S. D. Walck, A. V. Davydov, J. A. Robinson and T. G. Ivanov, *Appl. Phys. Lett.*, 2017, **111**, 051602.

- [3] P. Yan, Q. Tian, G. Yang, Y. Weng, Y. Zhang, J. Wang, F. Xie and N. Lu, *RSC Adv.*, 2018, **8**, 33193–33197.
- [4] J. Wang, H. Shu, P. Liang, N. Wang, D. Cao and X. Chen, *J. Phys. Chem. C*, 2019, **123**, 3861–3867.
- [5] B. Peng, G. Yu, X. Liu, B. Liu, X. Liang, L. Bi, L. Deng, T. C. Sum and K. P. Loh, *2D Mater.*, 2016, **3**, 025020.
- [6] R. D. Mahyavanshi, P. Desai, A. Ranade, M. Tanemura, G. Kalita, *ACS Appl. Electron. Mater.*, 2019, **1**(3), 302–310.
- [7] M. Moun, M. Kumar, M. Garg, R. Pathak and R. Singh, *Sci. Rep.*, 2018, **8**, 11799.
- [8] E. W. Lee, C. H. Lee, P. K. Paul, L. Ma, W. D. McCulloch, S. Krishnamoorthy, Y. Wu, A. R. Arehart and S. Rajan, *Appl. Phys. Lett.*, 2015, **107**, 103505.
- [9] S. Krishnamoorthy, E. W. Lee, C. H. Lee, Y. Zhang, W. D. McCulloch, J. M. Johnson, J. Hwang, Y. Wu and S. Rajan, *Appl. Phys. Lett.*, 2016, **109**, 183505.
- [10] K. Zhang, B. Jariwala, J. Li, N. C. Briggs, B. Wang, D. Ruzmetov, R. A. Burke, J. O. Lerach, T. G. Ivanov, M. Haque, R. M. Feenstra and J. A. Robinson, *Nanoscale*, 2018, **10**, 336–341.
- [11] R. D. Mahyavanshi, P. Desai, A. Ranade, M. Tanemura, G. Kalita, *ACS Appl. Electron. Mater.*, 2019, **1**(3), 302–310.
- [12] A. Thangaraja, S. M. Shinde, G. Kalita and M. Tanemura, *Mater. Lett.*, 2015, **156**, 156–160.